

Modified Reverse ADOR assembles Al-rich **UTL** zeolite from IPC-1P layers

Ondřej Veselý, Michal Mazur, Jan Přech, Jiří Čejka

Department of Physical and Macromolecular Chemistry, Faculty of Sciences, Charles University, Hlavova 8, 128 43 Prague 2, Czech Republic

Supplementary information

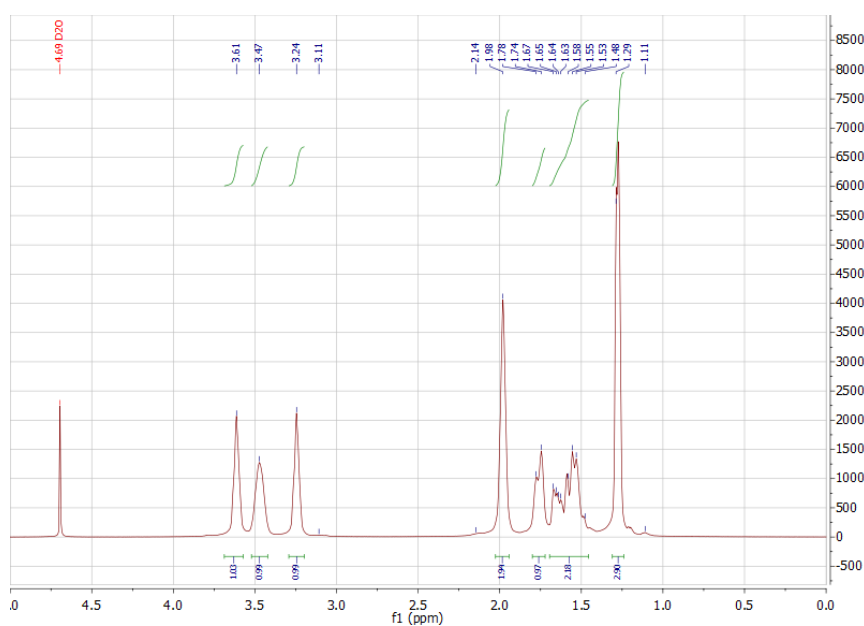


Fig. S1: ^1H NMR spectrum of the dimethyl-5-anizospiro[4.5]decane (DMASD) bromide in D_2O

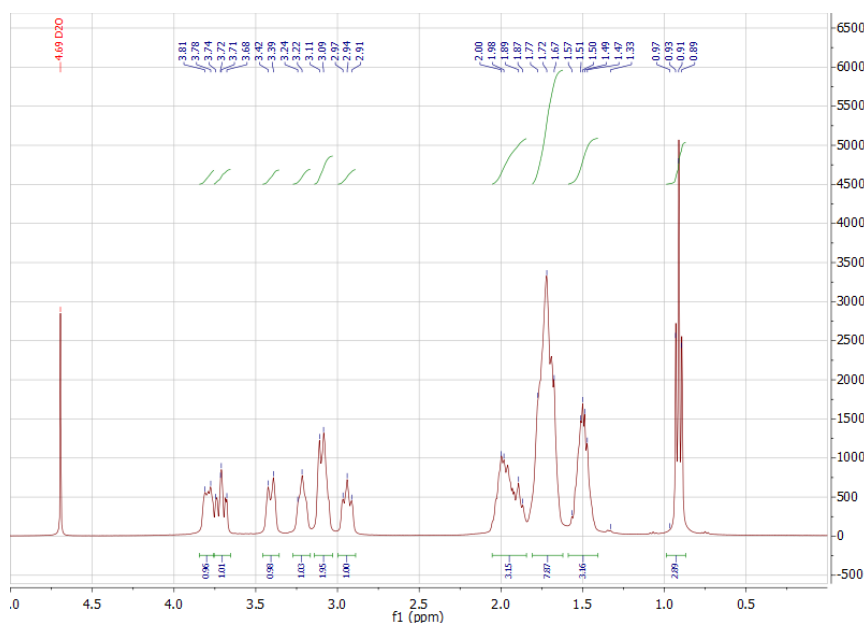


Fig. S2: ^1H NMR spectrum of the 7-ethyl-6-azoniaspiro[5.5]undecane (EASuD) bromide in D_2O

Table S1: Composition of synthesis mixtures for samples of reconstructed **UTL** samples

Sample	$C_{\text{HCl/EtOH}}$ (mol/l)	$\text{Me}_2(\text{EtO})_2\text{Si}$ (mg)	$(\text{MeO})_4\text{Ge}$ (mg)	NH_4F (mg)	$\text{Al}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ (mg)
3Si:1Al	1.25	49.4	0	2.1	41.6
1Si:1Al	1.25	32.9	0	2.1	83.3
1Si:3Al	1.25	16.5	0	2.1	124.9
Pure Al $\equiv$ pHCl = -0.1 (F)	1.25	0	0	2.1	166.5
pHCl = 1 (Ge)	10^{-1}	24.7	32.8	0	37.7
pHCl = 3 (Ge)	10^{-3}	24.7	32.8	0	37.7
pHCl = 5 (Ge)	10^{-5}	24.7	32.8	0	37.7
pHCl = 1 (F)	10^{-1}	50.9	0	2.1	37.7
pHCl = 3 (F)	10^{-3}	50.9	0	2.1	37.7
pHCl = 5 (F)	10^{-5}	50.9	0	2.1	37.7
Re-UTL (Al)	10^{-3}	50.9	0	2.1	37.7
Re-UTL (Al+Ge)	10^{-3}	24.7	32.8	0	37.7

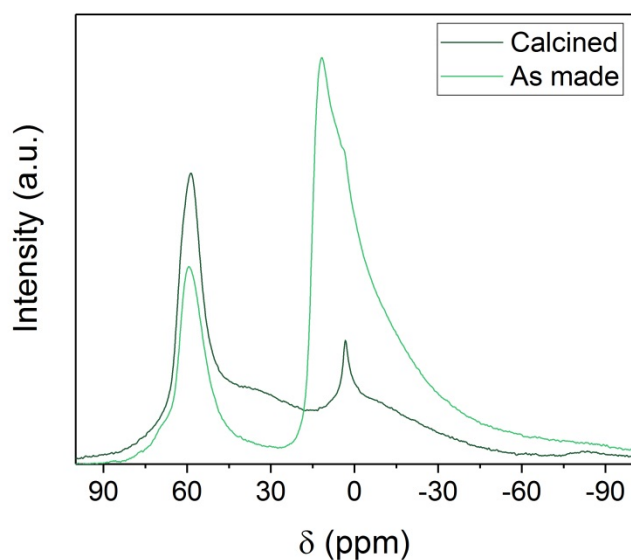


Fig. S3: ^{27}Al MAS MNR spectra of “pure Al” reconstructed **UTL** before and after calcination

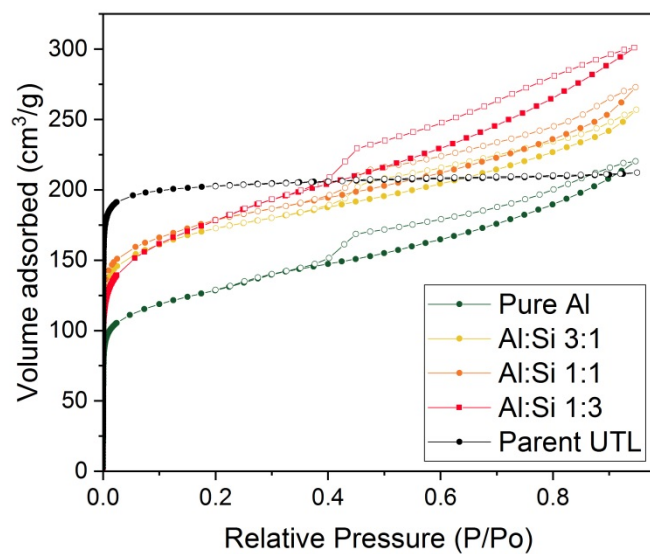


Fig. S4: Argon adsorption-desorption isotherms of **UTL** zeolites reconstructed with varying aluminium content

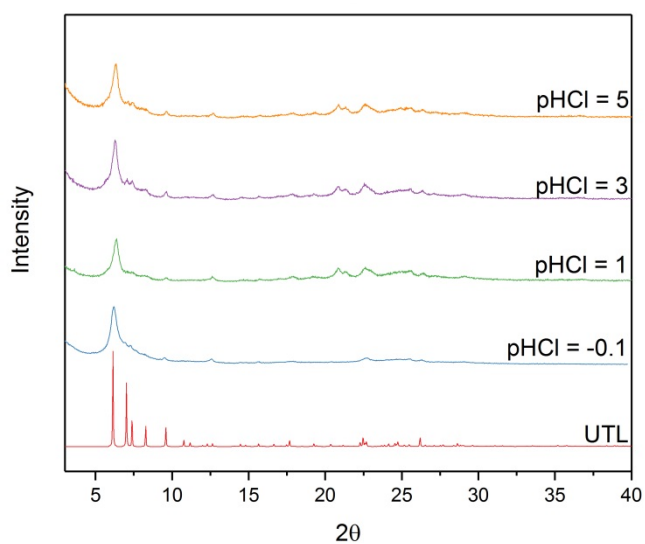


Fig. S5: Powder XRD patterns of **UTL** zeolites reconstructed by fluoride-assisted Reverse ADOR under varying acidity

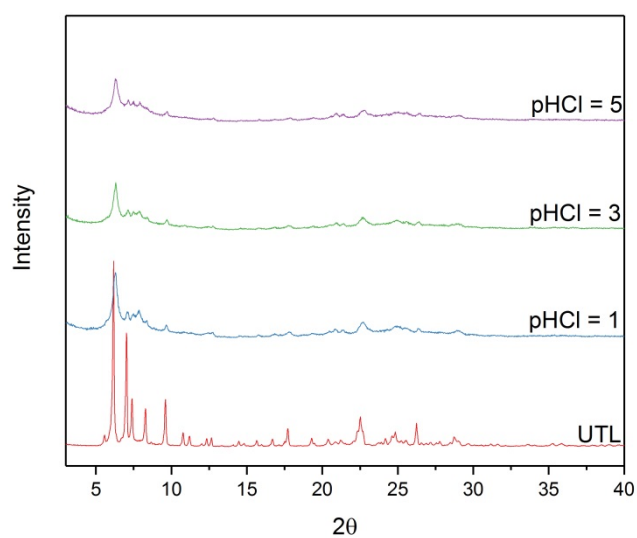


Fig. S6: Powder XRD patterns of **UTL** zeolites reconstructed by germanium-assisted Reverse ADOR under varying acidity

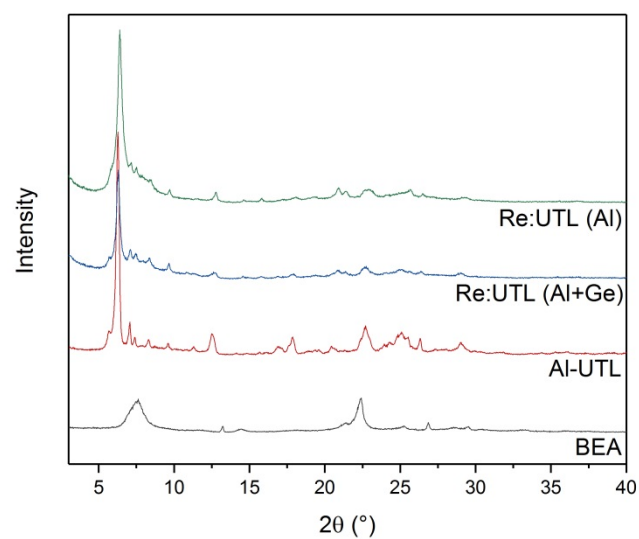


Fig. S7: Powder XRD patterns of **BEA**, Al-UTL and reconstructed **UTL** zeolites

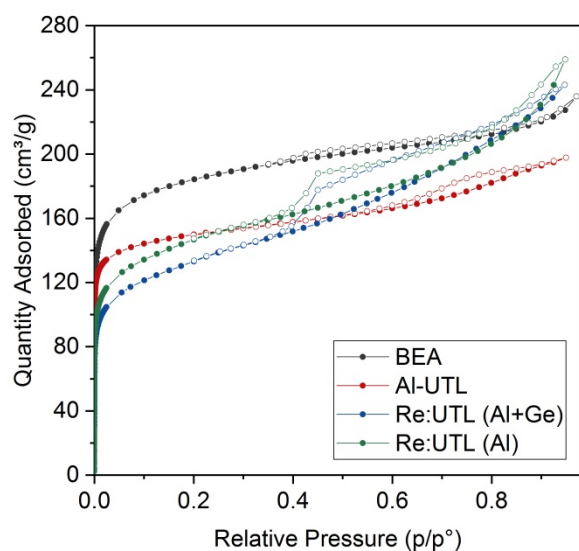


Fig. S8: Argon adsorption-desorption isotherms of **BEA**, Al-UTL and reconstructed **UTL** zeolites

Table S2: Textural and acidic properties of **BEA**, Al-UTL and reconstructed **UTL** zeolites

	BET (m ² /g)	S _{ext} (m ² /g)	V _{tot} (cm ³ /g)	V _{mic} (cm ³ /g)	C _{Brønsted} (μmol/g)	C _{Lewis} (μmol/g)
BEA	560	170	0.30	0.16	300	100
Al-UTL	454	64	0.25	0.15	46	74
Re-UTL (Al+Ge)	409	180	0.31	0.08	25	75
Re-UTL (Al)	450	138	0.33	0.09	21	54