

Supporting Information

Self-assembled Lignin Nanoparticles produced from Elephant Grass Leaves enable Selective Inactivation of Gram-positive Microorganisms

Isabella C. Tanganini^{†,‡}, Camilla H. M. Camargos[§], Jennifer C. Jackson[†], Sandra R. Ceccato-Antonini[^], Camila A. Rezende[§], Andreia F. Faria^{,†}*

[†]Engineering School of Sustainable Infrastructure & Environment, Department of Environmental Engineering Sciences, University of Florida, Gainesville, FL, 32611-6540, USA

[‡] Department of Agribusiness, Food and Nutrition, University of São Paulo – USP, Piracicaba, São Paulo, Brazil

[§] Departamento de Físico-Química, Instituto de Química, Universidade Estadual de Campinas (UNICAMP), P.O. Box 6154, 13083-970, Campinas, São Paulo, Brazil

^{*}School of Fine Arts, Federal University of Minas Gerais – UFMG, Belo Horizonte, MG, 31270-901, Brazil

[^]Department of Agroindustrial Technology and Rural Socioeconomics, Federal University of São Carlos – UFSCar, Araras, São Paulo, Brazil

*Corresponding Author (E-mail: andreia.faria@essie.ufl.edu, Tel: 352-392-7104)

Supporting information contains 5 pages with 4 supplementary figures.

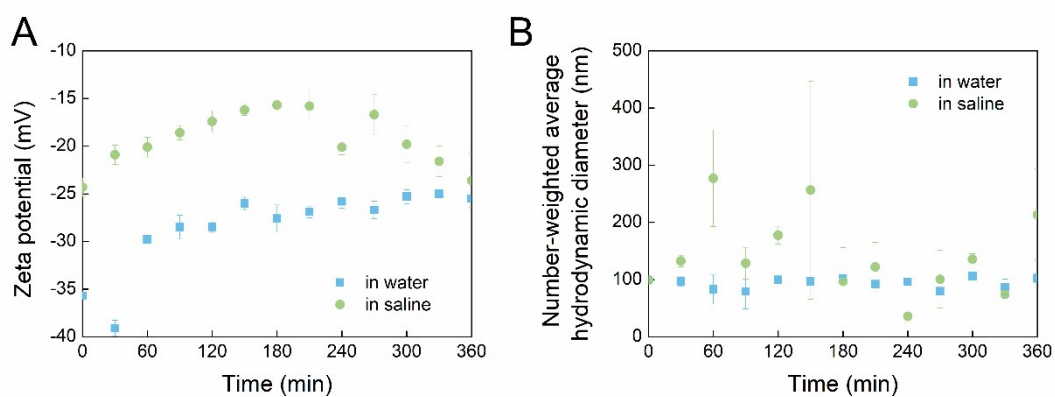


Figure S1. (A) Zeta potentials and (B) number-weighted average hydrodynamic diameters of SA-LNPs dispersed in deionized water or saline solution as a function of time. Measurements were taken over 6 h. Including all measurements, the mean zeta potentials were -28.5 ± 4.3 mV and -19.3 ± 2.9 mV, while the mean hydrodynamic diameters were 94 ± 9 nm and 142 ± 71 nm, respectively for SA-LNPs dispersed in water and saline.

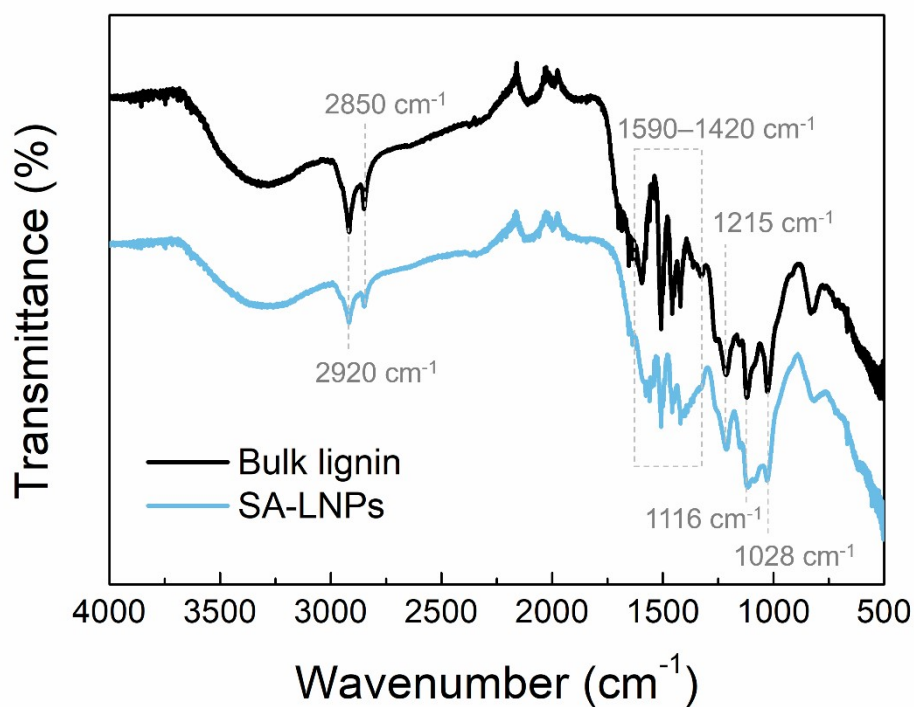


Figure S2. ATR-FTIR spectra of dried bulk alkaline lignin and SA-LNPs from elephant grass leaves. The absorption bands indicated by dotted lines are attributed to C–H stretching in methoxyl groups (2920 and 2850 cm^{-1}); C=C stretching in aromatic rings (1420 to 1590 cm^{-1}); C–O aryl-ether groups (1215 cm^{-1}), C=O stretching (1116 cm^{-1}), and aromatic C–H in-plane deformation (1028 cm^{-1}).

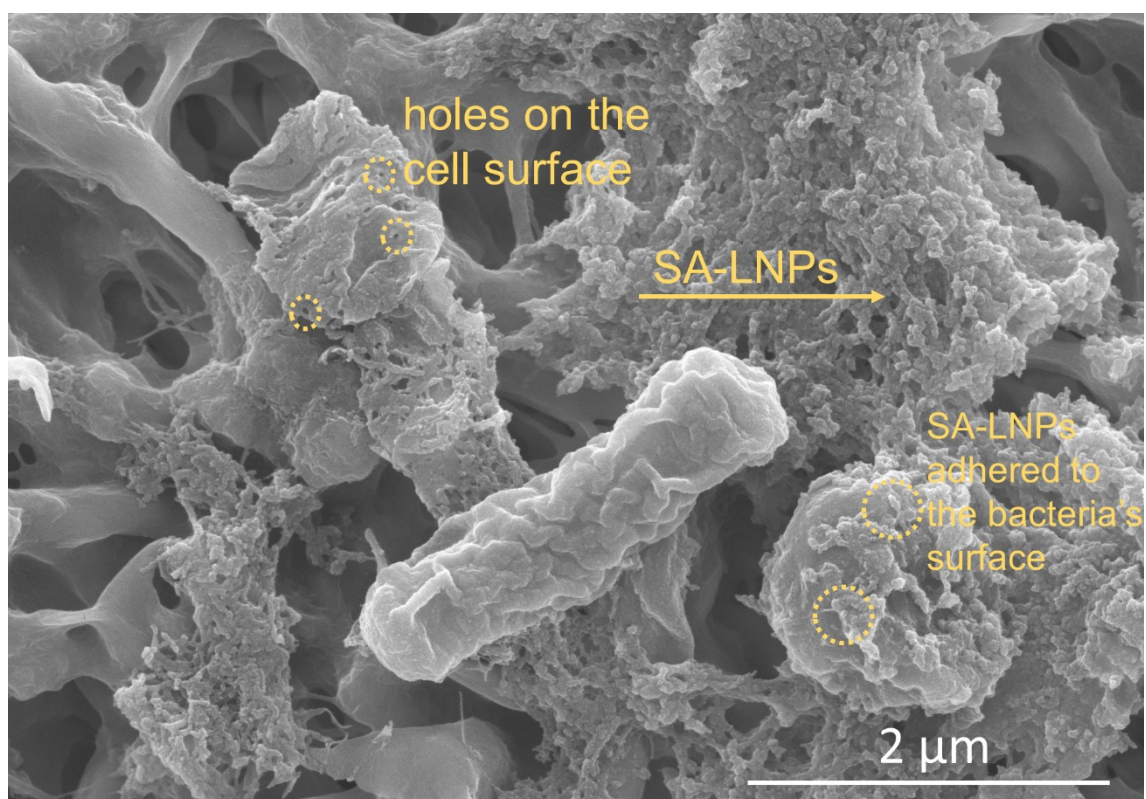


Figure S3: SEM image showing the formation of holes on the bacteria cell wall and adhesion of SA-LNPs on the surface of *L. fermentum* cells.

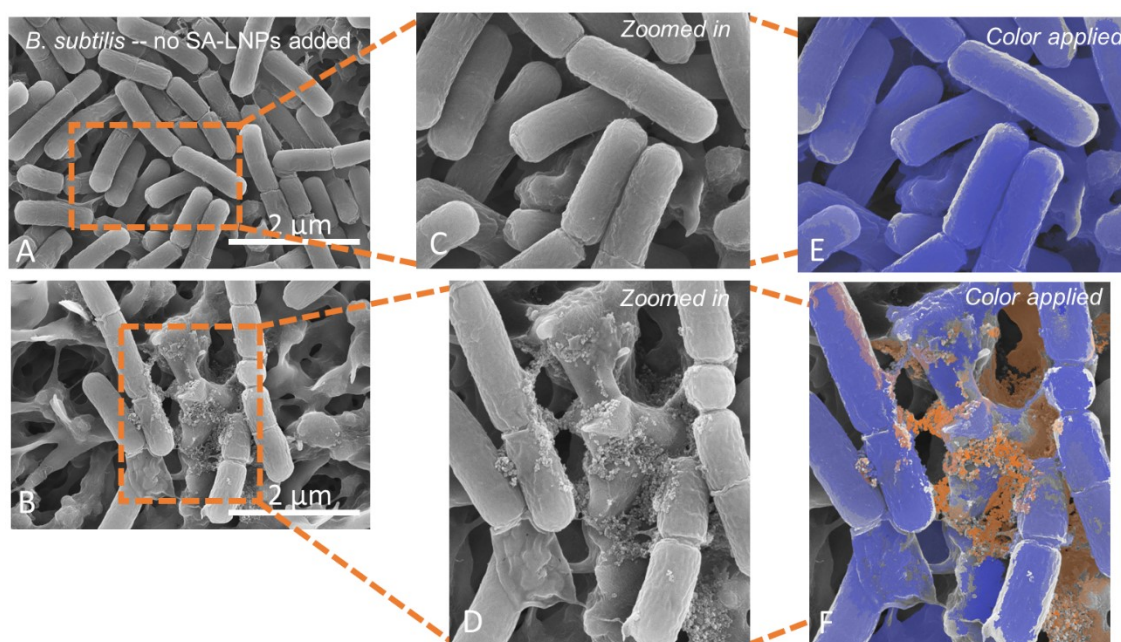


Figure S4: SEM images showing *B. subtilis* cells before (A) and after contact with SA-LNPs (B). Parts of the images were zoomed in (C and D) and color applied (E and F) to differentiate the cells in blue and the SA-LNPs in orange.

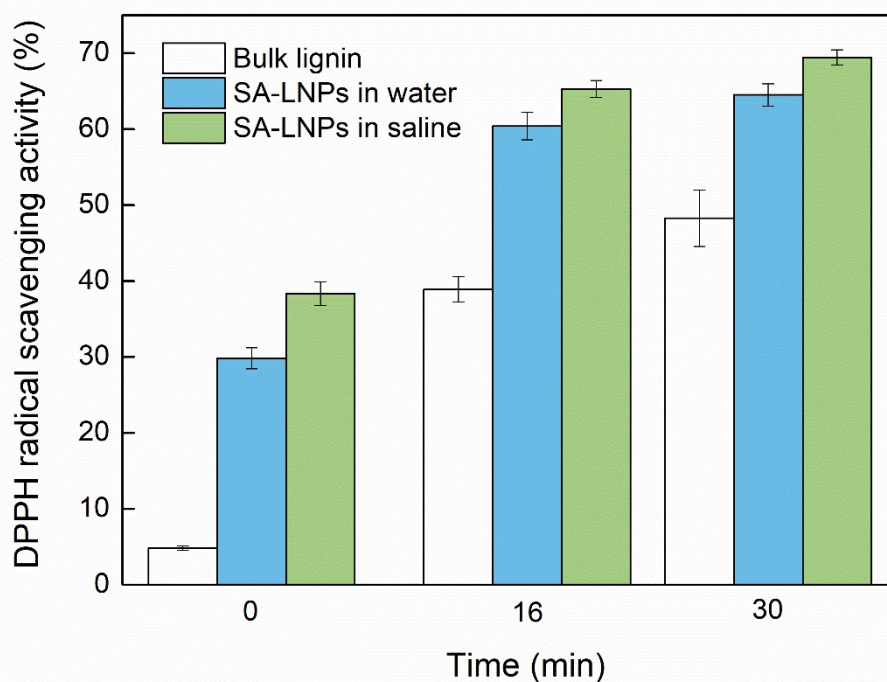


Figure S5. DPPH radical scavenging activity measured for bulk alkaline lignin dissolved in dioxane, SA-LNPs dispersed in deionized water, and SA-LNPs dispersed in saline solution. Antioxidant capacity assays were performed for 0, 16, and 30 min. After 30 min, the average scavenging activity was $48.3 \pm 3.7\%$ for bulk lignin, $64.5 \pm 1.7\%$ for SA-LNPs in water, and 69.5 ± 1.0 for SA-LNPs in saline. Lignin and SA-LNPs were tested at $50 \mu\text{g/mL}$.